

Quantum Charge Liquid - a new metallic state in 2 dimensions ? Application to $\text{Na}_{0.7}\text{CoO}_2$ family

G. Baskaran
Institute of Mathematical Sciences
C.I.T. Campus, Chennai 600 113, India

‘Quantum Charge Liquid’(QCL), a new phase, is proposed to describe anomalous metallic properties ($T \lesssim 100$ K) of a density ‘ y ’ of doped holes with strong coulomb repulsions, in a band insulator NaCoO_2 with N sites. This phase, a quantum melted charge order, is characterized by a ‘charge only’ fermi-sea (cFS) of yN charges and a ‘soft spin-liquid’ of yN spin- $\frac{1}{2}$ moments forming an ‘effective lattice’ of Heisenberg antiferromagnet. An approximate microscopic theory and some consequences are outlined. Anomalous ‘Fermi surfaces’ seen in ARPES of $\text{Na}_{0.5}\text{CoO}_2$ and $\text{Na}_{0.7}\text{CoO}_2$ matches well with our cFS, rather than a corresponding single band free electron FS.

Metallic solids exhibit a rich variety of symmetry broken phases such as, superconductivity, antiferromagnetism, ferromagnetism, charge density wave etc. In addition they also exhibit a variety of ‘normal state phases’. without any obvious symmetry breaking. A popular and ubiquitous normal state in metal physics is Landau’s fermi liquid state [1] that has been dominating the field for the past several decades. With the advent of lower dimensional conductors there has been a paradigm shift and novel metallic states such as Luttinger liquid in 1D [2], tomographic Luttinger liquid and a variety of quantum spin liquids with charges in 2D [3], quantum critical states [4] and others have come to the scene. Theories of these new metallic states often involve some exotic quantum world and modern mathematical ideas; at the same time they are believed to have far reaching implications for the real world through nano-technology and devices.

The aim of the present paper is to suggest a normal metallic state, in the temperature below about 100 K, called quantum charge liquid (QCL) in $\text{Na}_{1-y}\text{CoO}_2$, a quasi two dimensional metal [5]. Our motivation arises primarily, from among a variety of anomalies [6–14], a contrasting metal like quasi-particles (with a significantly expanded fermi surface !) seen in ARPES and an insulating type Curie-Weiss spin susceptibility.

Our working hypothesis is that there is a microscopically homogeneous single quantum liquid that exhibits the above anomalous behavior. We define a QCL state in a band insulator containing a density ‘ y ’ of doped electrons (or holes), living in a single band with coulomb repulsions. In a QCL, the underlying electrons become spin less fermions and condense into some kind of charge fermi sea (cFS). The yN spin- $\frac{1}{2}$ moments ‘riding’ on the charges form a weakly interacting soft (vanishingly small spin propagation velocity) non-condensed bose fluid of spin- $\frac{1}{2}$ moments in an effective Heisenberg lattice. Phenomenologically, QCL in $\text{Na}_{1-y}\text{CoO}_2$ seem to arise from a quantum melting of certain frustrated charge ordered states.

A schematic ‘normal state phase diagram’ for a 2D narrow band metal is shown in figure 1, where the suggested

QCL appears well away from the Mott insulating end. It is also interesting to note a kind of duality that exists between charges and spins between the ends of the phase diagram. In contrast, in a 1D narrow band metal we have only a Luttinger liquid phase. In the context of cuprates there has been attempts, notably by Putikka and collaborators [15] looking for spin less fermions, close to the Mott insulating end; they however find hard core boson as a more appropriate description, consistent with our phase diagram. An earlier work [16], with no long range coulomb interaction, found a different normal state phase diagram.

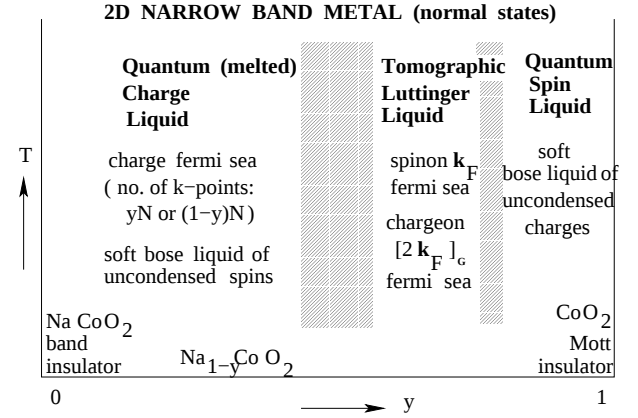


FIG. 1. Schematic ‘Normal State Phase diagram’ of a 2D narrow band metal. The proposed QCL appears away from the Mott insulating end; y is the carrier (holes in the case of $\text{Na}_{1-y}\text{CoO}_2$) density. A type of ‘duality’ between charges and spins at both ends is visible. Shadow denotes a crossover.

Our QCL hypothesis explains the shapes and area of the ARPES fermi surfaces [10,12] in a satisfactory fashion and some of the other features qualitatively, making the idea worth pursuing further. To this end, we focus on a one band model introduced by us [17] for $\text{Na}_x\text{CoO}_2 \cdot y\text{H}_2\text{O}$, a new superconductor [14] and formulate the QCL hypothesis first in terms of a variational wave function and then a slave fermion representation. To gain more understanding and motivate further anal-

ysis we also present a Landau type energy functional.

There are many striking anomalies in the experimental results in $\text{Na}_{1-y}\text{CoO}_2$ for $0.5 \gtrsim y \gtrsim 0.25$: i) Curie-Weiss behavior of uniform spin susceptibility [7–13], and non-Korringa $\frac{1}{T_1}$ behavior [11] in Na-NMR ii) a large thermoelectric power [6], which is easily suppressed [8] by small external magnetic fields ~ 10 T iii) temperature dependent Hall constant and a high temperature linear T behavior [9], iv) $\rho_{ab} \sim T$ or $T^{1-\epsilon}$ over a temperature range $0 \lesssim T \lesssim 100$ K and low c-axis conductivity [8,9,13], v) Large fermi surface radii seen in ARPES [10,12], too large compared to the non interacting fermi surface. vi) charge orderings as inferred from NMR/NQR [7,11].

Our model for $\text{Na}_{1-y}\text{CoO}_2$ is a single orbital tight binding model on a triangular lattice with yN hole carriers added to a band insulator NaCoO_2 . Even though the first LDA calculation [18] showed more than one band at the fermi level for $\text{Na}_{0.5}\text{CoO}_2$, we work with our earlier single band hypothesis [17], that has support from ARPES [10,12] and recent LDA + U calculations [21,20]. That is, in our modelling, in NaCoO_2 each Co^{3+} site is an orbitally non-degenerate spin singlet. The doped ‘holes’ are orbitally non-degenerate Co^{4+} sites; they carry a spin- $\frac{1}{2}$ moment and a charge e^+ , with reference to a Co^{3+} site.

Two cases of interest to us are $\text{Na}_{0.5}\text{CoO}_2$ and $\text{Na}_{0.7}\text{CoO}_2$, corresponding to hole band at fillings 0.25 and 0.15. Both cases are away from the Mott insulating half filled band. Since the band fillings are low, unscreened short range coulomb interactions are important. Simple estimates, similar to the one made in reference [19] shows that the unscreened interactions are comparable in strength to the band width, making charge order very likely. For the commensurate cases $y = \frac{1}{3}, \frac{2}{3}$ and $\frac{1}{4}, \frac{3}{4}$ we get triangular lattice charge orders: $\sqrt{3} \times \sqrt{3}$ and 2×2 . However, charge order for an arbitrary ‘y’ is frustrated by strong commensurability effects of the triangular lattice and an equally important disorder potential from the dopant Na^+ layer. We suggest that the result is a quantum melting into a novel, nearly uniform and homogeneous metallic state, QCL. The quantum molten state will be dominated quantum delocalized defects (topological and non-topological) of these orders. We do not discuss the mechanism of quantum melting, but focus on the quantum melted state.

In our narrow band metal, in addition to the usual superexchange, multiparticle exchange processes riding on local charge order correlations in the quantum melted state are likely to be present. We put them together and write an effective single band projected model:

$$H_{tJ} = -t \sum_{\langle ij \rangle} C_{i\sigma}^\dagger C_{j\sigma} + H.c. + J \sum_{\langle ij \rangle} (\mathbf{S}_i \cdot \mathbf{S}_j - \frac{1}{4} n_i n_j) + \sum_{ij} V_{ij} n_i n_j + \sum_i \epsilon_i n_i \quad (1)$$

with a local constraint $n_i \equiv n_{i\uparrow} + n_{i\downarrow} \neq 2$ of no double occupancy of holes; it means projecting out Co^{5+} states. Here C ’s are hole operators and $\mathbf{S}$ ’s spin operators. Since we use hole operators, in contrast to reference [17], the sign of the hopping matrix element is positive. The values of various parameters [17] are $t \approx 0.1$ eV, $J \approx 7$ meV; the screened near and next nearest neighbor coulomb repulsion parameters are $V_1 \approx 0.8$ eV and $V_2 \approx 0.4$ eV. And ϵ_i is a random potential arising from the Na^+ layer. A simple estimate shows that the root mean square fluctuation of ϵ_i can be as large as $\sqrt{\langle \epsilon_i^2 \rangle} \approx 0.2$ eV. In the absence of disorder and incommensurability effects the above model will exhibit charge order [19] for the range of doping $0 < y < 0.5$, with an energy scale of the order of 100 - 300 K, as the coulomb scale is comparable to the band width. Experimentally we see a metallic behavior, indicating a quantum molten state; any charge ordering signal seen in NMR/NQR [7,11] is likely to be very small in amplitude. This needs to be studied further.

The above is a hard many body problem, containing disorder and strong interaction. As a first step in gaining some understanding, we propose a variational wave function for our phenomenologically motivated (non-random) QCL state in coordinate representation:

$$\Psi_{\text{QCL}}[\mathbf{r}_i \sigma_i] \sim \Psi_{\text{ch}}(\mathbf{r}_1, \dots, \mathbf{r}_{yN}) \chi_{\text{spin}}(\mathbf{r}_1 \sigma_1, \dots, \mathbf{r}_{yN} \sigma_{yN}) \quad (2)$$

Here $\mathbf{r}_i$ denotes the lattice site of the hole and σ_i , the z-component of its spin. The charge function Ψ_{ch} is anti-symmetric and the spin function χ_{spin} symmetric, making Ψ_{QCL} antisymmetric. We choose Ψ_{ch} to be a simple slater determinant of a charge fermi sea(cFS) times a Jastrow factor:

$$\Psi_{\text{ch}}(\mathbf{r}_1, \dots, \mathbf{r}_{yN}) \sim \prod_{i < j} f(r_{ij}) \sum_P (-1)^{N_P} e^{i \sum_l \mathbf{k}_l \cdot \mathbf{r}_{Pl}} \quad (3)$$

where P stands for permutation of the particle indices, $N_P = 1$ (0) for odd (even) permutation. And $\mathbf{k}_l$ denote N_y k-points inside the charge fermi sea. We choose a form of $f(r_{ij})$ that gives us a quantum melted liquid of charges, with some short range charge order correlations.

The spin part of the wave function is a bose fluid of spin- $\frac{1}{2}$ moments - a soft spin liquid state (RVB) without any long range magnetic order

To discuss the low energy physics of QCL wave functions we find it convenient to use slave fermion representation, $C_i^\dagger = e_i s_{i\sigma}^\dagger$ with anti-commutation relations for the fermionic charges $\{e_i, e_j^\dagger\} = \delta_{ij}$ and commutation relation for the bosonic spins $[s_{i\sigma}, s_{j\sigma'}^\dagger] = \delta_{ij} \delta_{\sigma, \sigma'}$. Our Hamiltonian (equation 1) becomes:

$$H_{tJ} = t \sum_{\langle ij \rangle} e_j^\dagger e_i s_{i\sigma}^\dagger s_{j\sigma} + H.c. - J \sum_{\langle ij \rangle} b_{ij}^\dagger b_{ij} + \sum_{ij} V_{ij} e_i^\dagger e_i e_j^\dagger e_j, \quad (4)$$

Here $b_{ij} = \frac{1}{\sqrt{2}} \sum_{\sigma} \sigma C_{i\sigma} C_{j\sigma}$. An early slave-fermion [23] mean-field theory for a 2D t-J model on a square lattice (with no short range coulomb interaction) focussed on a ferromagnetic solution for nearly all y and $J \ll t$. We are however interested in understanding anomalous normal state and hence do not focus on symmetry broken ground states such as charge and or magnetically ordered states in the present paper.

Notice the change in sign of the hopping term in the slave-fermion representation, in contrast to the slave-boson representation. Within the Hilbert space of the our variational wave functions the charge dynamics is easily represented by an approximate effective charge ($\tilde{e}_i^\dagger, \tilde{e}_i$) Hamiltonian:

$$H_{ch} \approx \tilde{t}\chi_0 \sum \tilde{e}_i^\dagger \tilde{e}_j + H.c. \\ \approx \sum [2\tilde{t}\chi_0(\cos k_x + 2 \cos \frac{k_x}{2} \cos \frac{\sqrt{3}}{2} k_y) - \mu] \tilde{e}_k^\dagger \tilde{e}_k \quad (5)$$

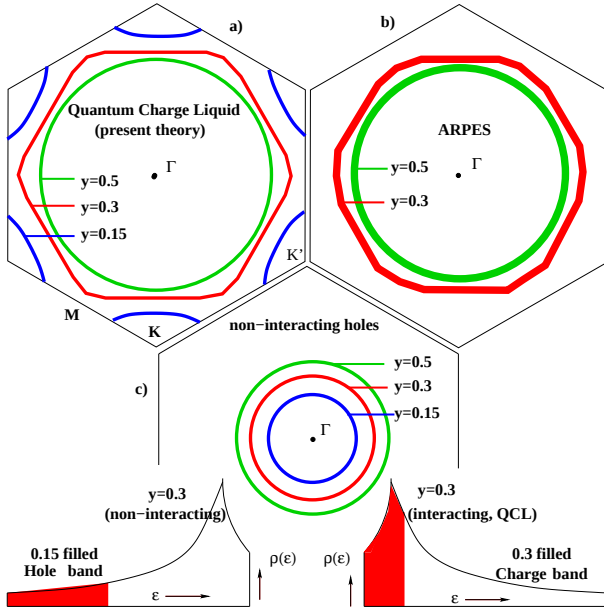


FIG. 2. Fig 2a) Charge Fermi surface of QCL for different fillings ($y = 0.5, 0.3, 0.15$; green, red and blue). 2b) An approximate sketch of ARPES Fermi surfaces of reference [10] and [12] for $y = 0.5$ and 0.3 , which are strikingly close to our cFS of figure 2a. 2c) Corresponding free hole Fermi surfaces, in our single band model ($y = 0.5, 0.3, 0.15$; green, red and blue). Bottom inset gives density of states and band filling of for $y = 0.3$ case: left - non-interacting hole band with filling 0.15 ; right - charge band of QCL with filling 0.3 . Notice the flip of the charge band and doubling of filled area.

The Jastrow factor and the ensuing short range charge order correlation renormalizes the hopping integral, $t \rightarrow \tilde{t}$. The spin-back flow also renormalizes the charge dynamics through $\chi_0 \approx \langle \sum_{\sigma} s_{i\sigma}^\dagger s_{j\sigma} \rangle$. Both $\tilde{t}$ and χ_0 may be formally computed as many body averages with respect to the QCL wave function. In the present paper

we do not attempt to calculate $\tilde{t}\chi_0$, but consider them as parameters to be determined from experiments; we estimate this to be $\tilde{t}\chi_0 \sim 1-10$ meV from existing experiments [8–13].

Let us discuss the consequence of the renormalized charge fermion Hamiltonian. Because of the sign of the hopping term, the band bottom of the charge fermions are at the K and K' points in-contrast to the holes whose band bottom is at the Γ point, leading to a flip in the density of states (figure 2). The shapes of the charge fermi sea (cFS) are shown in figure 2a for three values of $y = 0.5$ (green), 0.3 (red) and 0.15 (blue). It is very interesting that our cFS are close to (about 5 to 10 % larger) the ARPES results (figure 2b) for $y = 0.3$ and 0.5 including the hexagonal distortion that is present for $y = 0.3$ and absent for $y = 0.5$. For comparison the corresponding free fermi surface of yN holes with spins, in the single band model is shown in figure 2c for the three fillings. If our single band modeling is correct, correlation has indeed made a remarkable change. *Further the usual Luttinger theorem is violated and there seems to be a new Luttinger theorem and Luttinger volume containing yN or $(1-y)N$ k -points.*

Even though there is a nominal factorization of charge and spin subsystems in our wave function (equation 2), similar to the Ogata-Shiba wave function [22] in the $U = +\infty$ 1D Hubbard model, actual dynamics is performed by electrons or holes that carry both charge and spin. In view of this, experimentally measured quantities or physical (gauge invariant) correlation functions are convolutions of certain charge averages and spin averages, representing the strong back flow constraints accompanying a ‘charge’ or ‘spin’ motion. So a nominal charge fermi surface that is present in the charge part of our variational wave function may be completely washed out on convolution.

In the absence of any hard many body calculation we interpret the presence of ‘quasi-particle’ peak in ARPES and its near coincidence with our charge fermi surface, to imply that the back flow constraints do not wash the charge fermi surface completely. That is, an electron Greens function may be approximated by a convolution of charge and spin green function. Symbolically,

$$G(\text{electron}) \approx \sum_{\text{convolution}} G(\text{charge}) \times G(\text{spin}) \quad (6)$$

In a spin charge separated system depending on the dominance of the singularity of $G(\text{charge})$ or $G(\text{spin})$ the $G(\text{electron})$ will exhibit the corresponding singularity. For example in cuprates, $G(\text{spin})$ has a stronger singularity than the nearly incoherent and soft $G(\text{charge})$, leading to the observed ‘electron fermi surface’ albeit with power law singularities of the spectral functions, reflecting the non-fermi liquid behavior. In QCL we expect $G(\text{charge})$ to be more singular than the nearly incoherent and soft

G(spin), leading to the observed ‘charge Fermi Surface’. It will be interesting to investigate further the non-fermi liquid spectral function of electron in QCL using ARPES.

The spin part of the wave function is a bose fluid of spin- $\frac{1}{2}$ moments - a soft spin liquid state (RVB) without any long range magnetic order. Let us discuss the spin dynamics within the Hilbert space of our variational wave functions. Since we have a overdoped case, the superexchange is considerably reduced $J \rightarrow y^2 J$ (y^2 is the probability of finding two spins, Co^{4+} on neighboring sites); further the nearest neighbor short range repulsion encourages certain multiparticle exchange processes within the fluctuating charge ordered regions. The relatively fast charge dynamics allows us to average over dominant charge configurations and define a fictitious lattice (containing yN sites) of weakly interacting spin- $\frac{1}{2}$ moments, in the spirit of Born-Oppenheimer approximation. These moments have a Heisenberg antiferromagnetic coupling $J_{\text{eff}} \approx J y^2 + J_1 < J$. Here J_1 represents effective exchange couplings arising from other processes. The effective spin Hamiltonian of this fictitious lattice containing yN sites is :

$$H_{\text{spin}} \approx J_{\text{eff}} \sum_{\langle lm \rangle} \mathbf{S}_l \cdot \mathbf{S}_m \quad (7)$$

The above spin Hamiltonian is meaningful in getting any kind of response of the system at length scales $\ell \gg \frac{1}{\sqrt{y}}$, where $\frac{1}{\sqrt{y}}$ is the mean inter-hole distance in units of the lattice parameter. In the same fashion the above spin Hamiltonian is also meaningful only for time scales $\tau \gg \frac{\hbar}{t\chi_o}$, the hole delocalization time scale.

As mentioned earlier, for $y = \frac{1}{3}$ and $\frac{1}{4}$ charge ordered state are the triangular lattices: $\sqrt{3} \times \sqrt{3}$ and 2×2 . We take these lattices as the lattice of the fictitious Heisenberg spins, in trying to understand fillings close to 0.5 and 0.7. The above frustrated spin system has interesting spin liquid physics.

The high temperature limit of the above spin Hamiltonian may be thought of as a classical gas of spins- $\frac{1}{2}$ moments, suggested in reference [8] that carry the spin entropy in the thermopower measurements (through back flow) and also determines the Curie-Weiss susceptibility seen in experiments. In this sense J_{eff} may be also determined from the existing experimental results. Our estimate of this from experiments [7–13] is $J_{\text{eff}} \sim 1$ meV.

All the above considerations also leads in a natural way to a Landau like microscopic energy functional for our QCL:

$$E[\{n_{\mathbf{k}}\}; \{\mathbf{S}_l\}] \approx \sum_{\mathbf{k}} \epsilon_{\mathbf{k}}^{\text{ch}} n_{\mathbf{k}} + \sum_{\mathbf{k}} f_{\mathbf{k}, \mathbf{k}'} n_{\mathbf{k}} n_{\mathbf{k}'} + J_{\text{eff}} \sum (\mathbf{S}_l \cdot \mathbf{S}_m - \frac{1}{4}) \quad (8)$$

Here $\epsilon_{\mathbf{k}}^{\text{ch}}$ is the energy of the charge carrying quasi-particles and $f_{\mathbf{k}, \mathbf{k}'}$ are the Landau parameters, which

may also be singular for the ‘chargons’. Various Landau parameters can be treated as a phenomenological parameters, to be determined experimentally.

To summarize, the metallic state in $\text{Na}_{1-y}\text{CoO}_2$ with reasonably defined quasi particle, as seen in ARPES, and coherent transport occurring over a narrow temperature interval of about $0 \lesssim T \lesssim 100$ K has been identified with a novel Quantum Charge Liquid. Insulating like Curie-Weiss spin susceptibility gets naturally explained. We also find that the Hall constant in our theory is negative, consistent with the experimental observation [9], over the above temperature range. There has been experimental signals [24] for magnetic phase transitions at low temperatures in $\text{Na}_{1-y}\text{CoO}_2$. QCL can support low temperature symmetry broken states, including chiral metallic phase [17].

We believe that the idea of QCL may have a wider applicability: i) certain $\frac{1}{4}$ filled 2D organic conductors, ii) overdoped cuprates ($\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$) with $x \geq 0.4$, (if it can be synthesized) and iii) metal-insulator transition in 2D in the presence of interaction and disorder.

I thank Debanand Sa and R. Shankar for discussions.

-
- [1] D. Pines, Many Body Theory, W.A. Benjamin, inc. (1962)
 - [2] F.D.M. Haldane, J.Phys.C **14** 2585 (81)
 - [3] P.W. Anderson, The Theory of Superconductivity in the High T_c Cuprates, Princeton University Press (1997)
 - [4] S. Sachdev, Quantum Phase Transitions, Cambridge University Press (1999)
 - [5] T. Tanaka, S. Nakamura and S. Iida, Jpn. J. Appl. Phys. **33** L581 (94); C. Delmas, C. Fouassier and P. Hagenmuller, J. Sol.St. Chem., **13** 165 (75)
 - [6] I.Terasaki et al., Phys. Rev. **B 56** R 12685 (97)
 - [7] R. Ray et al., Phys. Rev. **B 59** 9454 (99)
 - [8] Y. Wang et al., Nature, **423** 425 (03)
 - [9] Y. Wang et al., cond-mat/0305455
 - [10] T. Valla et al., Nature, **417** 627 (02)
 - [11] J. L. Gavilano et al., cond-mat/0308383
 - [12] M.Z. Hasan et al., cond-mat/0308438
 - [13] M. Bruhwiler et al., cond-mat/0309311
 - [14] K. Takada et al., Nature, **422** 53 (03)
 - [15] W.O. Putikka, M.U. Luchini and R.R.P. Singh, Phys. Rev. Lett., **81** 2966 (98); cond-mat/9912269
 - [16] F. Basco et al., J. Phys. Soc. Jpn. **65** 687 (96)
 - [17] G. Baskaran, Phys. Rev. Lett., **91** 097003 (03)
 - [18] D. J. Singh, Phys. Rev. **B 61** 13397 (00)
 - [19] G. Baskaran, cond-mat/0306569
 - [20] L.J. Zou, J.L. Wang and Z. Zeng, cond-mat/0307560
 - [21] J. Kuneš et al., cond-mat/0308388
 - [22] M. Ogata and H. Shiba, Phys. Rev. **B41** 2326 (90)
 - [23] C. Jayaprakash, H. R. Krishnamurthy and S. Sarker, Phys. Rev. **B40** 2610 (89)
 - [24] I. Tsukuda et al., J. Phys. Soc. Japan, **70** 834 (01); T. Motohashi et al., Phys. Rev. **B 67** 064406 (03)